

## THE EFFECT OF GLASS INSULATION ON THE DEFORMATION OF THE MICROWIRE CORE

S.I. Ryabtsev<sup>1</sup>, V.F. Bashev<sup>2</sup>, O.I. Kushnerov<sup>1</sup>, T.V. Kalinina<sup>2</sup>, V.I. Fokin<sup>2</sup>, T.M. Dorozhka<sup>2</sup>

<sup>1</sup>*Oles Honchar Dnipro National University, Dnipro, Ukraine*

<sup>2</sup>*Dnipro State Technical University Kamianske, Dnipropetrovsk region, Ukraine*

*\*e-mail: sirybts@gmail.com*

**The influence of the elastic deformation of the b side of the glass insulation on the state of the metal core of the microwire (MW) was studied. It was shown that the structural state of the MW core is affected not only by the processes of non-equilibrium crystallization and heat removal conditions, but also by the application of stresses to the core from the side of the insulation in the process of drawing the MW.**

**Keywords:** microwires, microstructure, phase composition, melt-quenching, microhardness

Received 10.10.2024; Received in revised form 05.11.2024; Accepted 15.11.2024

### 1. Introduction

The creation of new materials with high functional characteristics and methods for their production is one of the main tasks. The development of modern information, nano- and biotechnologies depends on its solution. In recent decades, researchers have paid much attention to materials with an extremely nonequilibrium amorphous structure [1-2]. Modern methods of quenching from a liquid or vapor state, such as obtaining microwires by rapid crystallization, laser processing, electrochemical deposition, three-electrode ion-plasma sputtering, extreme plastic deformation [3-7], have significantly increased the number of substances obtained in a non-crystalline state. Cast amorphous glass micro- and nanowires are very interesting materials both from the point of view of theory and from the point of view of practical application. A simple technology for obtaining cast amorphous glass micro- and nanowires was first presented in 1924 by Taylor. This method was significantly modified by Ulitovsky in the period 1950-1964. The modified Taylor–Ulitovsky method allows the production of large batches of such microwires. Interest in cast glass microwires has increased significantly over the past few years, mainly due to their technological application as sensor elements in various devices [2,3]. The production of microwires by the Taylor–Ulitovsky method and the study of their magnetic properties have been the subject of numerous publications by various research groups [2–4, 8-10]. The main feature of microwires obtained by the quenching method from the liquid state is the simultaneous rapid solidification of the glass-coated metal alloy [8–10]. Therefore, other families of amorphous magnetic wires obtained by the so-called “rotational quenching in water” or melt extraction methods have distinctive magnetic properties, since their magnetoelastic anisotropy and magnetic domain structures are different. It is very interesting to consider the possibilities of the Taylor–Ulitovsky method to produce cast glass microwires, which can have different microstructures and metal core compositions.

### 2. Experimental procedure

The crystal structures of the as-cast and melt-quenched (MQ) samples were characterized by X-ray diffraction (XRD) using a DRON-2.0 diffractometer with Fe K $\alpha$  radiation. The XRD patterns were analyzed using the QualX2 software for qualitative phase identification [11]. The microhardness was measured using a PMT-3 microhardness tester at a load of 100 g. The microstructures of the as-cast and MQ samples were revealed by etching with a solution of hydrochloric (10ml) and nitric (30ml) acids for 3-10 sec and observed using a NEOPHOT-21 optical microscope.

### 3. Results and discussion

If we conditionally accept that the MW sample can have zero thickness, then it could be quenched without deformation at an infinite cooling rate. An increase in the thickness of the MW vein proportionally increases the hardening deformation; therefore, for a correct understanding of the processes that take place in MW, it is necessary to study in more detail the features of deformation in the place of contact between the vein and the glass, where, due to the difference in the thermal coefficients of their propagation, the highest stress level is observed. [12-14].

Calculations of stress and deformation at the interface " metal core-glass insulation " in the radial direction in MW were carried out by solving tasks Lamé [12]:

$$\sigma_r = \frac{E\omega\delta}{2\nu - \varphi + \omega(\psi - 2\nu)} \left(1 - \frac{c^2}{a^2}\right) \quad (1)$$

where  $\sigma_r$  is the stress at the radius of the conductor MW;

$E, \nu$  - Young's modulus and Poisson's ratio


$\varphi, \psi$  - equal, respectively,  $(1 + b^2/a^2)$ ,  $(1 + a^2/c^2)$  for outer layers and inner layers (Fig. 1)

$\delta$  - the amount of differential compression

In the case of MD, the coefficients in equation (1) can be written as:

$$\varphi = 1 + \frac{R^2}{r_{\text{жс}}^2}; \quad \psi = 1; \quad \omega = \frac{E_s}{E_l} \left(1 - \frac{R^2}{r_{\text{жс}}^2}\right);$$

$E_s, E_l$  - modulus of elasticity of glass and MW cores.

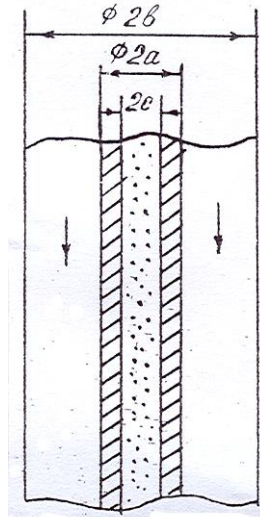

**Fig. 1. To determine the coefficients a, b, c.**

In tasks of this type, important attention should be paid to the value of differential compression:  $\delta = \alpha(T_n - T_k)$ ,  $\alpha$  - coefficient of temperature expansion;  $T_n, T_k$  - temperatures of the beginning and end of cooling. Since the coefficients of temperature expansion ( $\alpha$ ) of glass and alloys used in practice are average coefficients in a certain temperature range, in order to determine the deformations in the MW caused by the formation of the "glass-core material" junction, it is necessary to determine this total coefficient of temperature expansion for each temperature in the interval:  $T_n - T_k$ . The deformation of the MW core in the radial direction depends on its radius and, to a large extent, on the thickness of the insulation. Calculations

[4] show that an increase in the thickness of the insulation by 2 microns leads to an increase in the voltage on the core by 50...60%. That is, the formation of the vein structure takes place in a complex field of deformations: primarily due to the tension of the MW vein in the process of its extraction. The analysis [4] of calculations of MW deformations shows that in thin MWs, which are drawn at a high speed ( $> 150$  m/min), the core is subjected to high stress ( $> 7 \cdot 10^{-3}$  N), and therefore the latter significantly affects the final structure of the core.


The method of determining the residual stresses in the surface layer of the material without destroying the samples used in this work is based on X-ray structural determination of the exact period of its lattice (jointly with associate professor of DNU T.I. Anishchenko ). For this, MW segments were placed on the substrate in parallel rows. The X-ray picture was recorded in two positions of the sample: parallel and perpendicular to the beam. After measuring the interplanar distance in the crystals, the voltage was determined both in the direction and perpendicular to the axis of the MW core.

The elastic deformation in the surface layers of the sample in the direction perpendicular to the surface of the sample is determined by the formula (2) [15]

$$\varepsilon = (-\nu/E) \cdot (\sigma_1 + \sigma_2) \quad (2)$$

Where  $\sigma_1, \sigma_2$  are the tangential stresses to the surface of the sample

For further calculations, we will determine that if  $\sigma_1, \sigma_2$  it is a tensile stress, then  $\varepsilon$  it is a compression strain (Fig. 2).

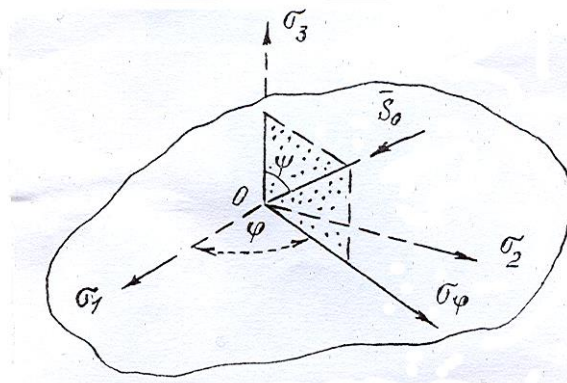


**Fig. 2. Angular relations between the principal stresses, the measured stress  $\sigma_\varphi$  and the coordinate axes  $x, y, z$  [15]**

To determine the deformation, it is necessary to find the value of the change in the interplanar distances  $d$  in the atomic planes parallel to the surface of the sample, since  $\varepsilon = \Delta d/d$ , then [15]

$$\sigma_1 + \sigma_2 = (-E/\nu) (\Delta d/d) \quad (3)$$

Experimentally, the task was reduced to radiographic determination of the magnitude of the relative deformation at different angles between the surface of the MW and the direction of the original beam. To determine the effect of insulation on the voltage that occurs in the core, samples were taken with and without glass insulation. In fig. 3. the profile of the line (311) from the MW (core diameter  $d_{wc} = 8 \mu\text{m}$ , insulation thickness  $\Delta = 4 \mu\text{m}$ ) from a single-phase alloy  $Ni_{94}Si_6$  (wt.%) is shown for the mentioned cases, from which it can be concluded that the interaction of the core and insulation during the cooling of the MW causes dynamic stresses in the core, which disappear after the insulation is removed (Table

1). Calculations show that the insulation causes additional stresses in the MW core of approximately  $\varepsilon = -0.0036$ , which disappear after annealing for 10 min. at 500 °C.

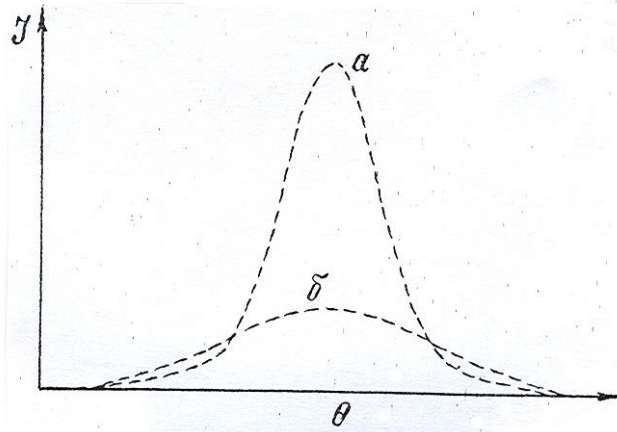

**Fig. 3. X-ray line profile (311) of MW alloy (wt.%) Ni<sub>94</sub>Si<sub>6</sub> : a) for a sample without insulation; b) for a sample with insulation.**

**Table 1. The position of the line (311) of the MW alloy depending on the shooting conditions ( Fe radiation)**

State	$\theta_{11}$	$\theta_L$	$\theta_{11}, \varphi=45^\circ$	$\theta_L, \varphi=45^\circ$
output with insulation	66.18	66.20	66.29	66.10
output without insulation	66.10	66.19	66.18	66.17
annealed with insulation	66.16	66.18	66.16	66.14
annealed without insulation	66.11	66.19	66.21	66.42

In order to establish the influence of the structure on the stresses that arise in the MW, X-ray structural studies were also carried out on samples of copper alloys (wt.%): 1st group - Cu - 30 Ni - 4.5 Si - 4.5 Mn ; 2-group - Cu - 30 Ni - 2.5 Si - 2.5 Mn .

The influence of insulation and heat treatment on stress was determined by stress components  $\sigma_\psi$  when the original beam was deflected by an angle  $\psi = 30^\circ$  in the normal plane.

Voltages of the 1st kind were determined by the formula [15]:

$$\sigma_\psi = \frac{(d_\psi - d)E}{d(1 + \nu)} \sin^{-2} \psi \quad (4)$$

where are  $d, d_\psi$ , respectively, interplane distances at angles  $90^\circ, 30^\circ$ .

The annealing mode was chosen so that no structural and phase transformations occurred during the heat treatment in the MW vein, which structurally consisted only of a supersaturated copper-based solid solution. The analysis of the data on the 1st kind of stresses shows that the chemical composition has a significant effect on the voltage in the MW vein: for example, an increase in silicon to 4.5% increases it by almost 2.7 times (Table 2).

**Table 2. Dependence of stresses of the 1st kind on heat treatment in MW of Cu-Ni-Si-Mn alloys**

Microwire	Stress, MPa			
	initial state		after heat treatment	
	with insulation	without insulation	with insulation	without insulation
<b>1 group</b>	<b>393</b>	<b>267</b>	<b>- 144</b>	<b>- 133</b>
<b>2 group</b>	<b>145</b>	<b>8</b>	<b>122</b>	<b>0</b>

**Note:**  $d_{\text{ж}}$ : MD = 10  $\mu\text{m}$ ,  $\Delta$  = 5  $\mu\text{m}$

Removing the insulation reduces the voltage, but the residual stresses in the first group continue to be greater than in the second, which can only be explained by the increased content of silicon. After heat treatment, the pattern of stress distribution in the listed groups of alloys is opposite, if in the 2nd group the stresses decrease, and after removing the insulation, the latter disappear, then in the first group, they change sign and remain significant even after the insulation is removed.

X-ray structural studies of the samples after high-temperature annealing made it possible to establish in the MW of the 1st group the release of complex silicide at the first stage  $(\text{Cu}, \text{Ni})_x \text{Si}_y$  with an as yet undetermined lattice. A similar behavior of stresses in the first group of MW can naturally be explained by the presence in the solid solution matrix of regions with a close arrangement of atoms, characteristic of this silicide.

During the MW study, it was also established that in the samples with 4.5% Si, the radiographs show a weakening of the interference lines with large indices associated with the influence of second-order stresses. In the work, this type of defectiveness is evaluated by the ratio  $(W = I_{311} / I_{111})$  intensity of the lines, showed that it practically does not depend on the composition of the alloys, but increases significantly (by 1.4-1.5 times) with an increase in the cooling rate, which proportionally affects the magnitude of the stresses of the second kind (micro-stresses,  $\Delta a / a$ ).

### Conclusions

1. The structural state of the MW vein is influenced not only by non-equilibrium crystallization processes and heat removal conditions, but also by the application of stresses of the first and second kind to it in the process of drawing the MW.
2. An increase in the amount of deformation helps to obtain a more uniform structure in the core of the microwire.

### References

1. **Fuks A.** The influence of internal stress on the nanocrystal formation of amorphous Fe<sub>73</sub>Si<sub>13</sub>B<sub>9</sub>1Cu<sub>1</sub>Nb<sub>3</sub>1 microwires and ribbons / A. Fuks, G. Abrosimova, O. Aksenov, M. Churyukanova, A. Aronin // Crystals. – 2022. – Vol. 12. – P. 1494–1505. [doi.org/10.3390/cryst12101494](https://doi.org/10.3390/cryst12101494)
2. **Talaat A.** Effect of annealing on magnetic properties of nanocrystalline Hitperm-type glass-coated microwires / A. Talaat, J. J. Del Vel, V. Zhukova, [et al.] // Journal of Alloys and Compounds. – 2016. – Vol. 6540. – P. 297–303. [doi.org/10.1016/j.jallcom.2015.11.102](https://doi.org/10.1016/j.jallcom.2015.11.102)
3. **Larin V. S.** Preparation and properties of glass-coated microwires / V. S. Larin, A. V. Torcunov, A. Zhukov, J. Conzales, M. Vasquez, I. Panina // Journal of Magnetism

- and Magnetic Materials. – 2002. – Vol. 249. – P. 39–45. DOI: 10.1016/S0304-8853(02)00501-2
4. **Baranov S. A.** Technology, preparation and properties of the glass-coated magnetic microphone wires / S. A. Baranov, V. S. Larin, A. V. Torcunov // *Crystals*. – 2017. – Vol. 7, № 6. – P. 136–142. doi.org/10.3390/cryst7060136
  5. **Bashev V.** Films of immiscible systems obtained by three-electrode ion-plasma sputtering / V. Bashev, O. Kushnerov, N. Kutseva, [et al.] // *Mol. Cryst. Liq. Cryst.* – 2021. – Vol. 721, No. 1. – P. 30 – 37. doi:10.1080/15421406.2021.1905274
  6. **Girzhon V.V.** Analysis of structure formation processes features in high-entropy alloys of Al-Co-Cr-Fe-Ni system during laser alloying/ V.V. Girzhon, V.V. Yemelianchenk, O.V. Smolyakov, [et al.]// *Results Mater.* -2022, Vol 15, P. 100311 - 100316. doi: 10.1016/j.rinma.2022.100311
  7. **Vasiliev S.V.** The effect of transient nucleation behavior on thermal stability of  $\text{Fe}_{48}\text{Co}_{32}\text{P}_{14}\text{B}_6$  metallic glass // S.V. Vasiliev, V.I. Parfenii, A.S. Aronin, E.A. Pershina, V.I. Tkatch // *J. Alloys Compd. (Journal of Alloys and Compounds)*, - 2021, Vol. 869, P. 159285-159290, doi.org/10.1016/j.jallcom.2021.159285
  8. **Zhukov A.** Correlation of Crystalline Structure with Magnetic and Transport Properties of Glass-Coated Microwires // A. Zhukov; M. Ipatov,; A/ Talaat; [et al.] // *Crystals* - 2017, Vol. 7 issu 2, P. 41-84. doi.org/10.3390/cryst7020041
  9. **Peng H.X.** Co-based magnetic microwire and field-tunable multifunctional macro-composites. // H.X. Peng; F.X. Qin; M.H. Phan; [et al.] // *J. Non-Cryst. Solids* - 2009, Vol. 355, P. 1380–1386 doi.org/10.1016/j.jnoncrysol.2009.05.040
  10. **Baranov S.A.** Domain structure of Fe-based microwires. // S.A. Baranov; D. Laroze; P. Vargas; M. Vazquez. // *Phys. B* - 2006, Vol. 372, P. 324–327 doi.org/10.1016/j.physb.2005.10.077
  11. **Altomare A.** Main features of QUALX2.0 software for qualitative phase analysis // A. Altomare, N. Corriero, C. Cuocci, [et al.] // *Powder Diffraction*, - 2017, Vol. 32(S1), P. 129-133; doi.org/10.1017/S0885715617000240
  12. **Lyubimov, M. L.** Splices of metal and glass / M. L. Lyubimov. – M.: GEI, 1957. – 258 p
  13. **Cline R.W.** Fundamentals of Glass-to-Metal Bonding: V, Wettability of Iron by Molten Sodium Disilicate // R.W. Cline, R.M. Fulrath, J.A.Pask // *Journal of the American Ceramic Society* - 1961. Vol.44. – Issue 9. - P. 423-428 https://doi.org/10.1111/j.1151-2916.1961.tb13749.x
  14. **Zhukov A.** Microwires coated by glass: A new family of soft and hard magnetic materials // A. Zhukov, J. Gonzalez, J.M. Blanco, [et al.] // *J. Mater. Res.* - 2000.-vol.15, N10. - p.2107-2113 doi.org/10.1557/JMR.2000.0303
  15. Mudryi S.I., Kulyk Yu.O., Yakymovych A.S. X-ray structural analysis in materials science. Teaching method. guide. – Lviv, I. Franko National University of Lviv 2017. – 114 p.